



## A preliminary study on sclerofoam morphology. *Étude préliminaire de la morphologie des mousses sclérosantes.*

Cosmi F.<sup>1</sup>, Biasi G.<sup>2</sup>

### Summary

An original experimental approach has been proposed, in which micro-tomography and morphological techniques have been successfully used to investigate the possibility and the significance of a morphology characterization of sclerofoams.

Several sclerofoams samples were prepared in different conditions and different concentrations of Polidocanol and immediately quickly frozen in liquid N<sub>2</sub> in order to avoid macro-crystals formation. Then, they were subjected to micro-tomography at the Tomolab facility of Elettra, Trieste.

The 3D reconstructions of the internal structures of the foams were successively analyzed and morphological parameters such as number, dimensions and degree of isotropy of the bubble structures obtained could be assessed.

The preliminary results obtained so far confirm that micro-tomography is a technique that can be successfully used to characterized the types of sclerofoam obtained with the different methods currently in use.

**Keywords:** sclerofoam, micro-CT, morphology, Quant3D, Pore3D.

### Résumé

Cette étude repose sur une approche expérimentale originale, utilisant des micro-tomographies et des techniques morphologiques ont pu être utilisées avec succès pour étudier la survenue et la signification de la caractérisation morphologique des mousses sclérosantes.

Plusieurs échantillons de mousses sclérosantes ont été préparés dans différentes conditions avec différentes concentrations de polidocanol. Elles ont été immédiatement congelées rapidement dans l'azote liquide afin d'éviter la formation de macro-cristaux. Ensuite, elles ont été soumises à la micro-tomographie grâce au Tomolab d'Elettra, Trieste. Les reconstructions 3D de la structure interne des bulles de mousse ont été successivement analysées et les paramètres morphologiques des structures obtenues ont pu être évalués : tels que le nombre, les dimensions et le degré d'isotropie de la bulle.

Les résultats préliminaires obtenus jusqu'à présent confirment que la micro-tomographie est une technique qui peut être utilisée avec succès pour caractériser les types de mousses sclérosantes obtenues pouvaient être évalués obtenus avec les différentes méthodes actuellement en usage.

**Mots-clés:** mousses sclérosantes, micro-CT, morphologie, Quant3D, Pore3D.

### Introduction

In the last years, foam sclerotherapy has been used widely in the treatment of the chronic venous insufficiency because it has permitted the cure of medium-small varicose veins but most importantly it has allowed the cure of the saphenous trunks.

UGFS (Ultrasound Guided Foam Sclerotherapy) is nowadays considered to be a valid substitution for the traditional surgery and for the other endovascular procedures (i.e. EVLA and radiofrequency) used in the treatment of the small and great saphenous vein.

During these last years, many authors have proposed different techniques to produce the foam and different concentration of the sclerosant drug to use depending on the diameter of the vein treated [1, 2, 3, 4, 5, 6, 7]. The method that is used more frequently is Tessari's [1].


This involves a 3 way connector and a mixture of sclerosant liquid (sodium tetradecyl sulfate 1-3% or polidocanol 0.25-0.50-1-3%) and gas (air) in the volumes proportion of 1:4. Progressively, the requirements for the fabrication of an effective and safe foam, have become more defined instead of spherical [8] bubbles.

1. Francesca Cosmi, University of Trieste, via A. Valerio 10, 34127 Trieste, Italy.

2. Giovanna Biasi, SOC Chirurgia Vascolare, Az. Ospedaliera Universitaria, Udine, Italy.

E-mail: [cosmi@units.it](mailto:cosmi@units.it)

Accepted le 8 juin 2011

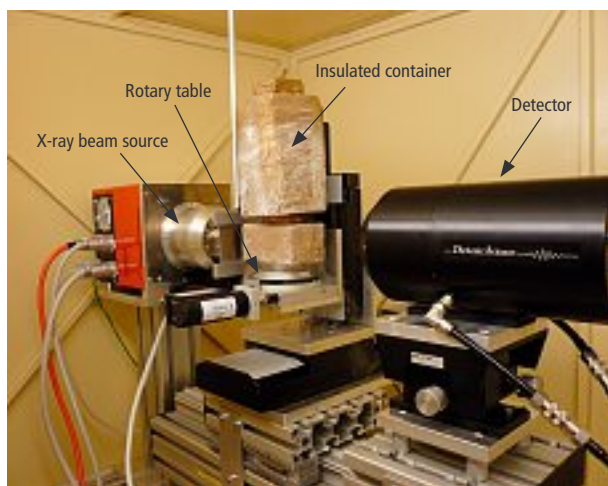

**FIGURE 1 :** The acquisition set-up at the Tomolab facility of Elettra (Trieste, Italy).

There have been several attempts to standardize the foam using different devices (Turbofoam, Sterivein).

Furthermore, different techniques for the foam injection and materials have been described by various authors.

The aim of this work is to investigate the possibility and the significance of a morphology characterization of sclerofoams obtained under different preparation conditions.


## Materials and Method

In this study, six sclerofoams samples were prepared in laboratory. According to the Tessari's method [13], we obtained the foam by mixing 20 or 50 times air and polidocanol drug (3% and 0.5% concentration) using two syringes and a three-way connector. Each foam was then injected in a Eppendorf tube using pipes of different dimensions (C1:  $1.3 \times 45$  mm and C2:  $0.3 \times 13$  mm) and immediately quick-frozen in liquid  $N_2$  to avoid macro-crystals formation while preserving the foam structure during the measurements.

A non-destructive definition of the frozen sample three-dimensional internal structure was obtained by X-ray micro-Computed Tomography. The set-up used at the Tomolab facility of Elettra (Trieste, Italy) achieves a spatial resolution of 10 micron.

The sample, contained in a insulated box, is placed on a rotating table and several projections are acquired at different angles over 180 degrees (**Figure 1**).

The 3D reconstructions (**Figure 2**) of the foams structures were analyzed and several morphological parameters such as number, dimensions and degree of isotropy of the bubble structures were computed [14, 15, 16].

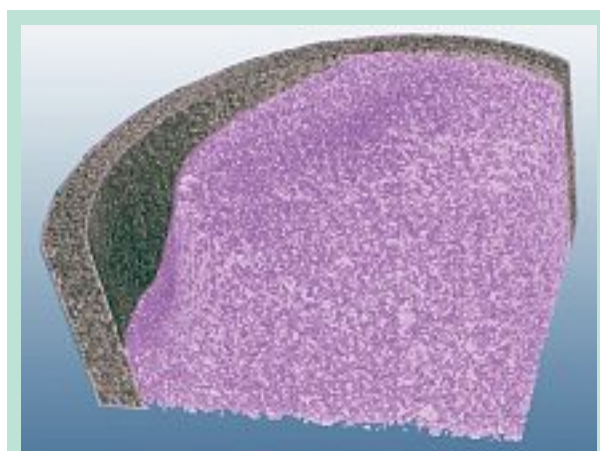

**FIGURE 2 :** A portion of the 3D reconstruction of a polidocanol foam (the external part of the tube is also visible).

## Experimental Results

Differences can be easily observed in the structures obtained with different foam preparation methods, for example by examining the samples tomographic sections shown in **Figure 3**.

The morphological analyses were conducted on a 2003 voxel volume extracted from the central portion of the samples.

A quantitative characterization of the different foam microstructures can be attained by computing the histograms of the bubbles volume and of the bubbles wall thickness (obtained by Pore3D [4] and by Quant3D [5] software respectively), as shown in **Figure 4** and **Figure 5**.

## Conclusions


An original experimental approach has been proposed, in which micro-tomography and morphological techniques have been successfully used to characterized the sclerofoams.

To our knowledge, this is also the first attempt to monitor sclerofoams for applied research purposes.


In this first step of the research, we were able to detect differences among the samples prepared in different conditions.

Nevertheless, in order to obtain quantitative results of clinical significance, a larger number of experimental observations is required and further work has already been planned.

A preliminary study on sclerofoam morphology.

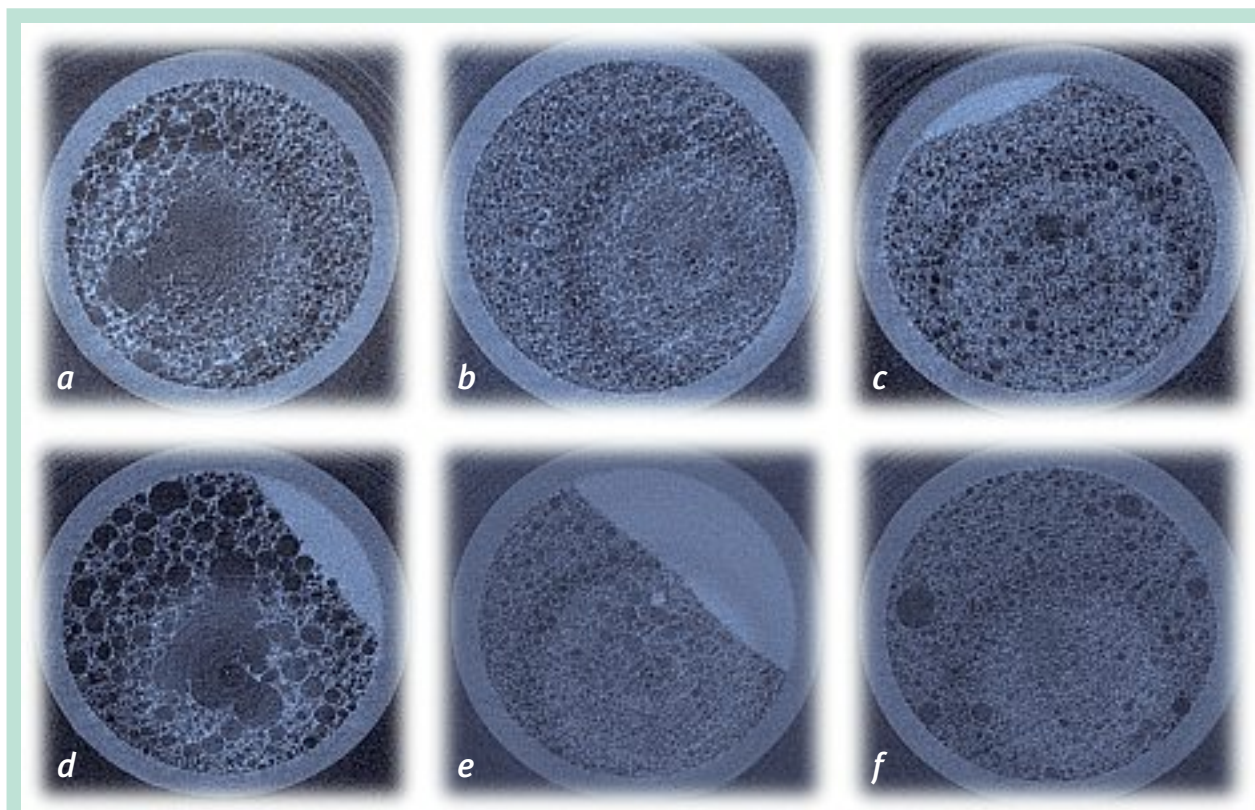

**FIGURE 3 :** Different foam structures obtained by varying the preparation parameters: (a) 3% 20 x C1; (b) 3% 20 x C1; (c) 0,5% 20 x C1; (d) 0,5% 50 x C1; (e) 0,5% 20 x C2; (f) 0,5% 50 x C2.

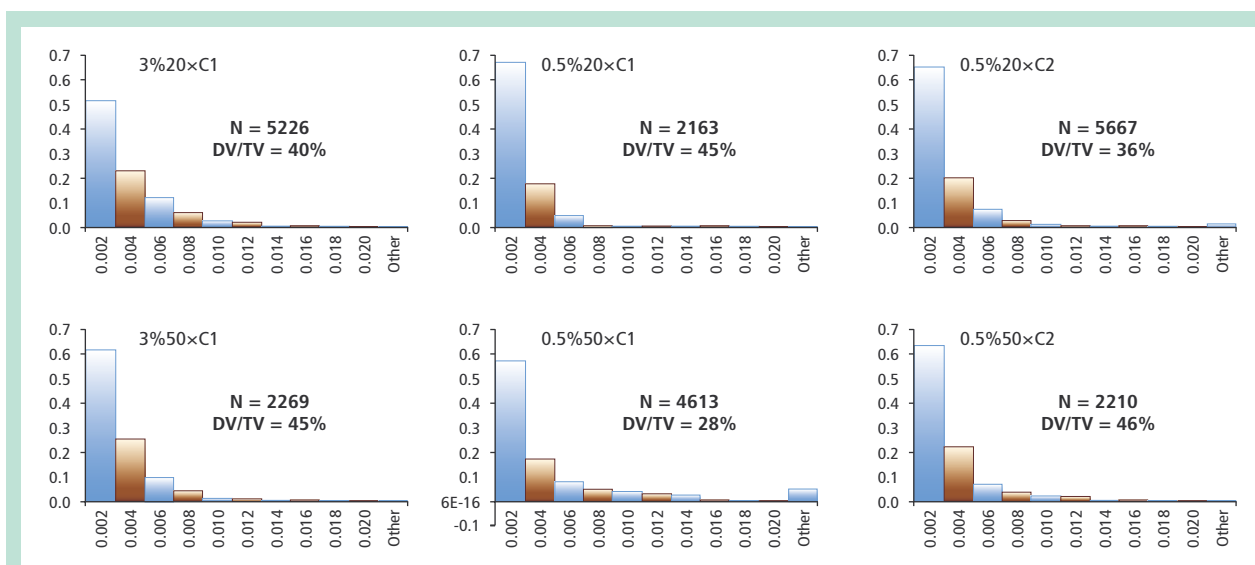

**FIGURE 4 :** Histograms of the bubbles volume.

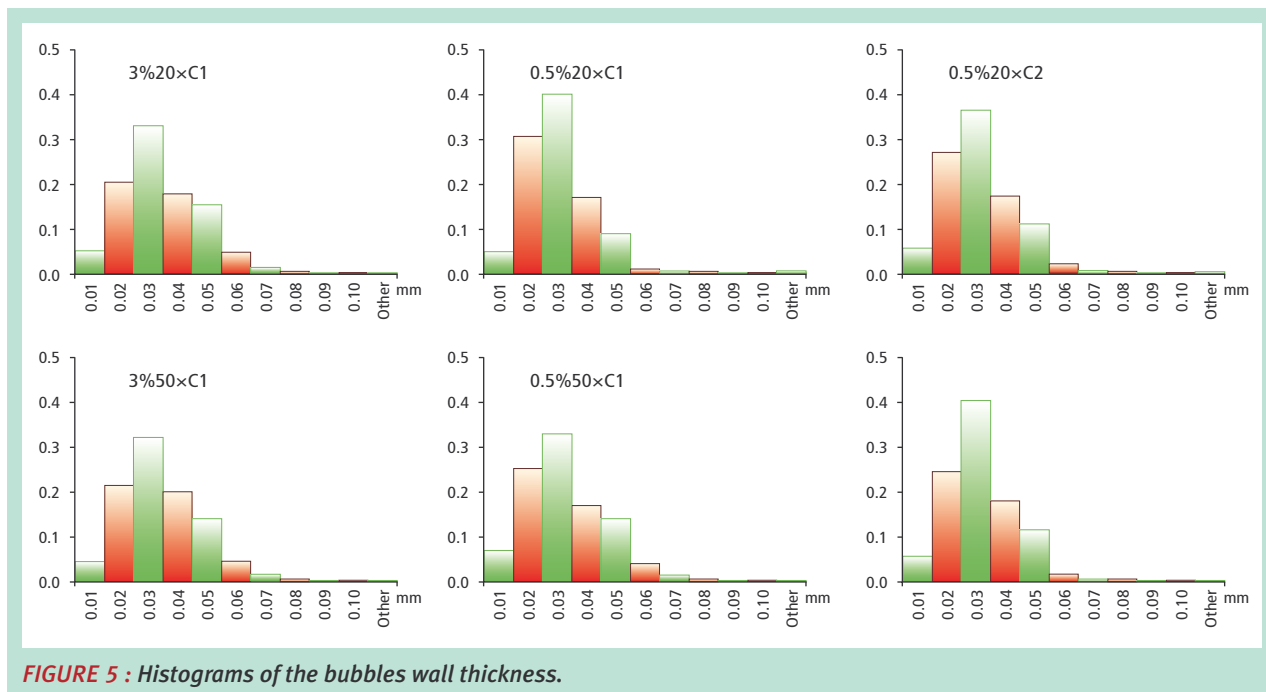


FIGURE 5 : Histograms of the bubbles wall thickness.

**Acknowledgements**

The Authors wish to thank S. Scozzese for assistance in sample preparation and experimental measurements. Samples quick-freeze and images acquisitions were possible thanks to the support of the Tomolab staff, in particular D. Dreossi and N. Sodini. Images reconstruction and Pore3D computations were conducted with the help of F. Brun and R. Cely Barroso.

**References**

- Tessari L., Cavezzi A., Rosso M., Cabrera G. Variables in foam sclerotherapy; literature and experimental data. A.N.Z.J. Phleb. 2008; 11: 83-4.
- Hamel-Desnos C., Allaert F.A., Benigni J.P., et al. Étude 3/1 mousse de polidocanol 3 %, versus 1 % dans la grande veine saphène : premiers résultats. Phlébologie 2005 ; 2 : 175-82.
- Cabrera J., Cabrera J. Jr. Nuevo metodo de esclerosis en las varices tronculares. Patologia Vasc. 1995; 4: 55-73.
- Cavezzi A., Tessari L. Foam sclerotherapy and techniques: different gases and methods of preparation, catheter versus direct injection. Phlebology 2009; 24: 247-51.
- Sica M. Guide pratique illustré pour réussir les traitements par sclérothérapie échoguidée à la mousse. Éditions Editcrea, 2009.
- Wollmann J. The history of sclerosant foams. Dermatol. Surg. 2004; 30: 694-703.
- Monfreux A. Traitement sclérosants des troncs saphéniens et leur collatérales de gros calibre par la méthode MUS. Phlébologie 1997 ; 50 : 351-3.
- Sadoun S. Critères pour la fabrication d'une mousse sclérosante de qualité. Phlébologie 2011 ; 64 : 26-31.
- Ferrara F., Bernbach H.R. Efficacité de la sclérothérapie à la mousse en fonction de l'aiguille utilisée. Phlébologie 2005 ; 58 : 229-34.
- Morrison N. Foam sclerotherapy, how to improve results and reduce side effects. Phlébologie 2009; 62: 23-34.
- Coleridge Smith P. Saphenous ablation: sclerosant or sclerofoam? Semin. Vasc. Surg. 2005; 18: 19-24. Review.
- Bergan J.J., Pascarella L. Severe chronic venous insufficiency: primary treatment with sclerofoam. Semin. Vasc. Surg. 2005; 18: 49-56. Review.
- Tessari L. Nouvelle technique d'obtention de la scléromousse. Phlébologie 2000 ; 53 : 129.
- Brun F., Mancini L., Kasae P., Favretto S., Dreossi D., Tromba G. Pore3D: A software library for quantitative analysis of porous media. Nuclear Instr. Meth. In Physics Research A 2010; 615: 326-32.
- Ketcham R.A. Three-dimensional grain fabric measurements using high-resolution X-ray computed tomography. J. Structural Geology 2005; 27: 1217-28.
- Smith T.H., Schneider E., Odgaard A. Star length distribution: a volume-based concept for the characterization of structural anisotropy. J. Microsc. 1998; 191: 249-57.